

# ***Cutting Shaping Data***

## ***Our soft magnetic alloys***

### **Introduction**

This brochure gives an overview of the data on lathing/ cutting, drilling, milling and grinding for our soft magnetic alloys. It covers our materials MUMETALL, PERMENORM 5000V5/5000H2, VACOFLUX 17 and hot worked VACOFLUX 50.

All these nickel-iron and cobalt-iron alloys, except VACOFLUX 50, are very tough in the soft, hot rolled state. Thus we recommend semi-finished products are purchased in the hard state whenever possible and machined in this state. However, in this case, owing to the size of the parts, the hot rolled state was selected. The tools and the machine settings used have been compiled in the following tables.

If very heavy machinery is available the cutting rates can be increased substantially, in particular when roughturning. In contrast, the cutting performance when finishing is largely governed by the specified tolerances and end-surface requirements.

The aim of this leaflet is to provide users with the relevant data on the most important soft magnetic alloys as a guideline for cutting-shaping processes. The tables should be of practical use to those working on site as they not only include nominal values but recommendations on tooling.

## Lathing

Reversible carbide tips, quality P10 - P30 were used for the tests. A low cutting speed and high feed rate were selected for roughturning. In contrast, for finishing the cutting rates are heavily dependent on the specified tolerances and the surface quality required. As a result, low feed and high cutting speed are implemented (see Table for details on feed and cutting speed).

Rings and discs are to be machined from the outside inwards - especially when working with VACOFLUX 50, or, prior to this, the edges are to be chamfered at 45° to avoid damage. The geometry of the reversible carbide tip to be used is also governed by the machining requirements (rough machining or finishing, surface quality, shape etc).

## Drilling

The cutting-shaping data with handfeed are based on a normal standard drill of the commonly used HSS quality. When drilling with automatic feed HSS drills with TiN coating were implemented.

With VACOFLUX 50 slight chipping of the edges may occur when the drill emerges through the material, we recommend drilling from both sides.

## Milling

When milling the material was pre-worked with a cutter head of 100 mm Ø at relatively high cutting speed. Then using the VHM milling head, Ø 16 mm (TiAlN) milling was completed with an appropriately low cutting speed.

Again VACOFLUX is prone to edge cracking and should be chamfered or machined towards the centre.

## Flat Grinding

When choosing a grinding disc for soft magnetic alloys a comparison can be made with hardened tooling steel, and the discs selected accordingly. Due to extreme heat development good cooling is crucial for the grinding discs.

VACOFLUX 50 may split at the edges and should be chamfered or machined from the outside inwards.

## Cooling

Greatest care must be taken over cooling and lubrication. Drilling oil emulsions are generally preferred; as a rule in accordance with DIN 6558 emulsions with 5 - 10% coolant oil are used. In all processing steps of the tests conducted a 5% cutting oil emulsion was employed

## Special Remarks

Whenever possible a cooling phase is to be introduced between pre and final machining steps to allow for (to neutralize) any expansion which might occur. Occasionally, pre-machining may affect the dimensional accuracy of the finished part. In special cases involving difficult, complex or thin walled work pieces or tight tolerances

the material can be run through a suitable intermediate annealing step, so-called stress relief heat treatment.

## Heat Treatment

After machining the parts must be cleaned thoroughly to remove impurities caused by lubrication.

The magnetic materials are then subjected to a final heat treatment to set the optimum magnetic properties. This final magnetic heat treatment step takes place after final shaping.

Alloy:	High Temperature annealing:
<b>MUMETALL:</b>	5hrs 1050°C, Cool in furnace to < 300°C. H <sub>2</sub> atmosphere.
<b>VACOPERM 100:</b>	5hrs 1150°C, Cool in furnace to < 300°C. H <sub>2</sub> atmosphere.
<b>PERMENORM 5000V5/5000H2:</b>	5hrs 1150°C, Cool in furnace to < 300°C. H <sub>2</sub> atmosphere.
<b>TRAFOPERM:</b>	5hrs 1150°C, Cool in furnace to < 300°C. H <sub>2</sub> atmosphere.
<b>VACOFLUX 50:</b>	10hrs 820°C, Cool in furnace to < 200°C. H <sub>2</sub> atmosphere.
<b>VACOFLUX 17:</b>	10hrs 850°C, Cool in furnace to < 200°C. H <sub>2</sub> atmosphere.

The data for PERMENORM can be used as a basis for VAC Expansion and Glass-to-Metal Sealing Alloys VACON 11/70, VACOVIT and VACODIL.

# Cutting - Shaping Data

Alloy: MUMETALL analysis: 76.6 % Ni / 4.5 % Cu / 3.3 % Mo / balance Fe				
Shaping	Cutting speed: V <sub>c</sub> (m/min)	Feed: f (mm/Umdreh.)	Tool:	Remarks:
Lathing <sup>1)</sup>	50 – 150	0.15 – 0.50	Tooling head: reversible carbide tip: quality: P 10 – P 30	Cutting dep.: a = 5 mm Coolant: 5 % cutting oil emulsion clear. angle: 7°
Cutting <sup>2)</sup>	50 – 150	0.05 – 0.2	Tool: Carbide cutting tip, coatet (Zinner: ZG 30) <sup>4)</sup>	Cutting dep.: a = 4 mm Coolant: 5 % cutting oil emulsion
Drilling <sup>3)</sup>	n = revs/min a.) 60 – 450 b.) 400 – 700	a.) handfeed b.) 0.05 – 0.15 (auto feed)	Tool: HSS drill a.) standard drill b.) standard drill with TiN coating	Coolant: 5 % cutting oil emulsion
Milling	a.) 150 – 250 b.) 40 – 80	fz = mm/cutting tooth a.) 0.05 – 0.15 b.) 0.02 – 0.1	a.) cutter head: 100 mm Ø P 10 – P 30 (round reversible blades) b.) VHM cutter: 16 mm Ø (TiAlN)	Coolant: 5 % cutting oil emulsion Slight increase in tip wear
Flat Grinding	surface meters: 32 (m/sec)	–	Grinding disc: 40A80L6V13 <sup>5)</sup> Abm.: 400x60x127 - DIN 69120 keep disc well cooled to prevent overheating	Cutting dep.: a = 0.005 mm Coolant: 5 % cutting oil emulsion Good surface

<sup>1+2)</sup> dimensions: 58 mm Ø

<sup>4)</sup> Zinner GmbH, Karl-Martell-Str. 35, 90431 Nürnberg

<sup>3)</sup> drill: 10.5 mm Ø

<sup>5)</sup> Krebs & Riedel, Bremer Str. 24, 34385 Bad Karlshafen

Alloy: PERMENORM 5000V5/5000H2 analysis: 47.5 % Ni / balance Fe				
Shaping	Cutting speed: V <sub>c</sub> (m/min)	Feed: f (mm/Umdreh.)	Tool:	Remarks:
Lathing <sup>1)</sup>	20 – 60	0.10 – 0.50	Tooling head: reversible carbide tip: quality: P 10 – P 30	Cutting dep.: a = 5 mm Coolant: 5 % cutting oil emulsion clear. angle: 7° Poor chip breaking
Cutting <sup>2)</sup>	50 – 150	0.10 – 0.20	Tool: Carbide cutting tip, coatet (Zinner: ZG 30) <sup>4)</sup>	Cutting dep.: a = 4 mm Coolant: 5 % cutting oil emulsion
Drilling <sup>3)</sup>	n = revs/min a.) 220 – 650 b.) 300 – 800	a.) handfeed b.) 0.05 – 0.25 (auto feed)	Tool: HSS drill a.) standard drill b.) standard drill with TiN-coating	Coolant: 5 % cutting oil emulsion
Milling	a.) 150 – 200 b.) 50 – 100	fz = mm/cutting tooth a.) 0.20 b.) 0.02 – 0.1	a.) cutter head: 100 mm Ø P 10 – P 30 (round reversible blades) b.) VHM cutter: 16 mm Ø (TiAlN)	Coolant: 5 % cutting oil emulsion Slight increase in tip wear a.) cutting dep.: ap = 2 mm b.) cutting dep.: ap = 10 mm
Flat Grinding	surface meters: 32 (m/sec)	–	Grinding disc: 40A80L6V13 <sup>5)</sup> size: 400x60x127 - DIN 69120 keep disc well cooled to prevent overheating	Cutting dep.: a = 0.005 mm Coolant: 5 % cutting oil emulsion Good surface

<sup>1)</sup> dimensions: 50 mm Ø

<sup>4)</sup> Zinner GmbH, Karl-Martell-Str. 35, 90431 Nürnberg

<sup>2)</sup> dimensions: 42 mm Ø

<sup>5)</sup> Krebs & Riedel, Bremer Str. 24, 34385 Bad Karlshafen

<sup>3)</sup> drill: 10.5 mm Ø

<b>Alloy: VACOFLUX 17</b>		<b>analysis: 17 % Co / 2.0 % Cr / balance Fe</b>		
Shaping	Cutting speed: V <sub>c</sub> (m/min)	Feed: f (mm/rev)	Tool:	Remarks:
<b>Lathing</b> <sup>1)</sup>	<b>50 – 150</b>	<b>0.15 – 0.50</b>	Tooling head: reversible carbide tip: Quality: P 10 – P 25	Cutting dep.: a = 5 mm Coolant: 5 % cutting oil emulsion Clear. angle: 7° Poor chip flow
<b>Cutting</b> <sup>2)</sup>	<b>50 – 150</b>	<b>0.05 – 0.20</b>	Tool: Carbide cutting tip, coatet (Zinner: ZG 30) <sup>4)</sup>	Cutting dep.: a = 4 mm Coolant: 5 % cutting oil emulsion
<b>Drilling</b> <sup>3)</sup>	n = revs/min <b>a.) 350</b> <b>b.) 200 – 1000</b>	<b>a.) handfeed</b> <b>b.) 0.05 – 0.30</b> (auto feed)	Tool: HSS drill a.) standard drill b.) standard drill with TiN coating	Coolant: 5 % cutting oil emulsion
<b>Milling</b>	<b>a.) 80 – 160</b> <b>b.) 40 – 100</b>	fz = mm/cutting tooth <b>a.) 0.05 – 0.20</b> <b>b.) 0.05 – 0.20</b>	a.) cutter head: 100 mm Ø P 10 – P 25 (round reversible blades) b.) VHM cutter: 16 mm Ø (TiAlN)	Coolant: 5 % cutting oil emulsion Edges crack easily
<b>Flat Grinding</b>	surface meters: <b>32</b> (m/sec)	–	Grinding disc: 40A80L6V13 <sup>5)</sup> size: 400x60x127 - DIN 69120 cool disc well	Cutting dep.: a = 0.008 mm Coolant: 5 % cutting oil emulsion

<sup>1)</sup> dimensions: 50 mm Ø

<sup>2)</sup> dimensions: 40 mm Ø

<sup>3)</sup> drill: 10.5 mm Ø

<sup>4)</sup> Zinner GmbH, Karl-Martell-Str. 35, 90431 Nürnberg

<sup>5)</sup> Krebs & Riedel, Bremer Str. 24, 34385 Bad Karlshafen

<b>Alloy: VACOFLUX 50</b>		<b>analysis: 49 % Co / 1.9 % V / balance Fe</b>		
Shaping	Cutting speed: V <sub>c</sub> (m/min)	Feed: f (mm/Umdreh.)	Tool:	Remarks:
<b>Lathing</b> <sup>1)</sup>	<b>50 – 150</b>	<b>0.10 – 0.40</b>	Tooling head: reversible carbide tip: quality: P 10 – P 25	Cutting dep.: a = 5 mm Coolant: 5 % cutting oil emulsion Clear. angle: 7° Poor chip breaking
<b>Cutting</b> <sup>2)</sup>	n = revs/min <b>50 – 500</b>	<b>0.05 – 0.15</b>	Tool: Carbide cutting tip, coatet (Zinner: ZG 30) <sup>4)</sup>	Cutting dep.: a = 4 mm Coolant: 5 % cutting oil emulsion Coolant heats up easily.
<b>Drilling</b> <sup>3)</sup>	n = revs/min <b>a.) 250 – 1000</b> <b>b.) 100 – 1250</b>	<b>a.) handfeed</b> <b>b.) 0.05 – 0.2</b> (auto feed)	Tool: HSS drill a.) standard drill b.) standard drill with TiN coating	Normal drills Coolant: 5 % cutting oil emulsion Slight fracturing of edges on drilling through.
<b>Milling</b>	<b>a.) 20 – 50</b> <b>b.) 20 – 50</b>	fz = mm/cutting tooth <b>a.) 0.10</b> <b>b.) 0.02 – 0.08</b>	a.) cutter head: 100 mm Ø P 10 – P 25 (round reversible blades) b.) VHM cutter: 16 mm Ø (TiAlN)	Coolant: 5 % cutting oil emulsion Edges crack, extreme wear of reversible cutting tip.
<b>Flat Grinding</b>	surface meters: <b>32</b> (m/sec)	–	Grinding disc: 40A80L6V13 <sup>5)</sup> size: 400x60x127 - DIN 69120 keep disc well cooled, long sparking-out period	Cutting dep.: a = 0.003 mm pro Zustellung Coolant: 5 % cutting oil emulsion Edges crack.

<sup>1)</sup> dimensions: 50 mm Ø


<sup>2)</sup> dimensions: 40 mm Ø

<sup>3)</sup> drill: 10.5 mm Ø

<sup>4)</sup> Zinner GmbH, Karl-Martell-Str. 35, 90431 Nürnberg

<sup>5)</sup> Krebs & Riedel, Bremer Str. 24, 34385 Bad Karlshafen

You will find us:

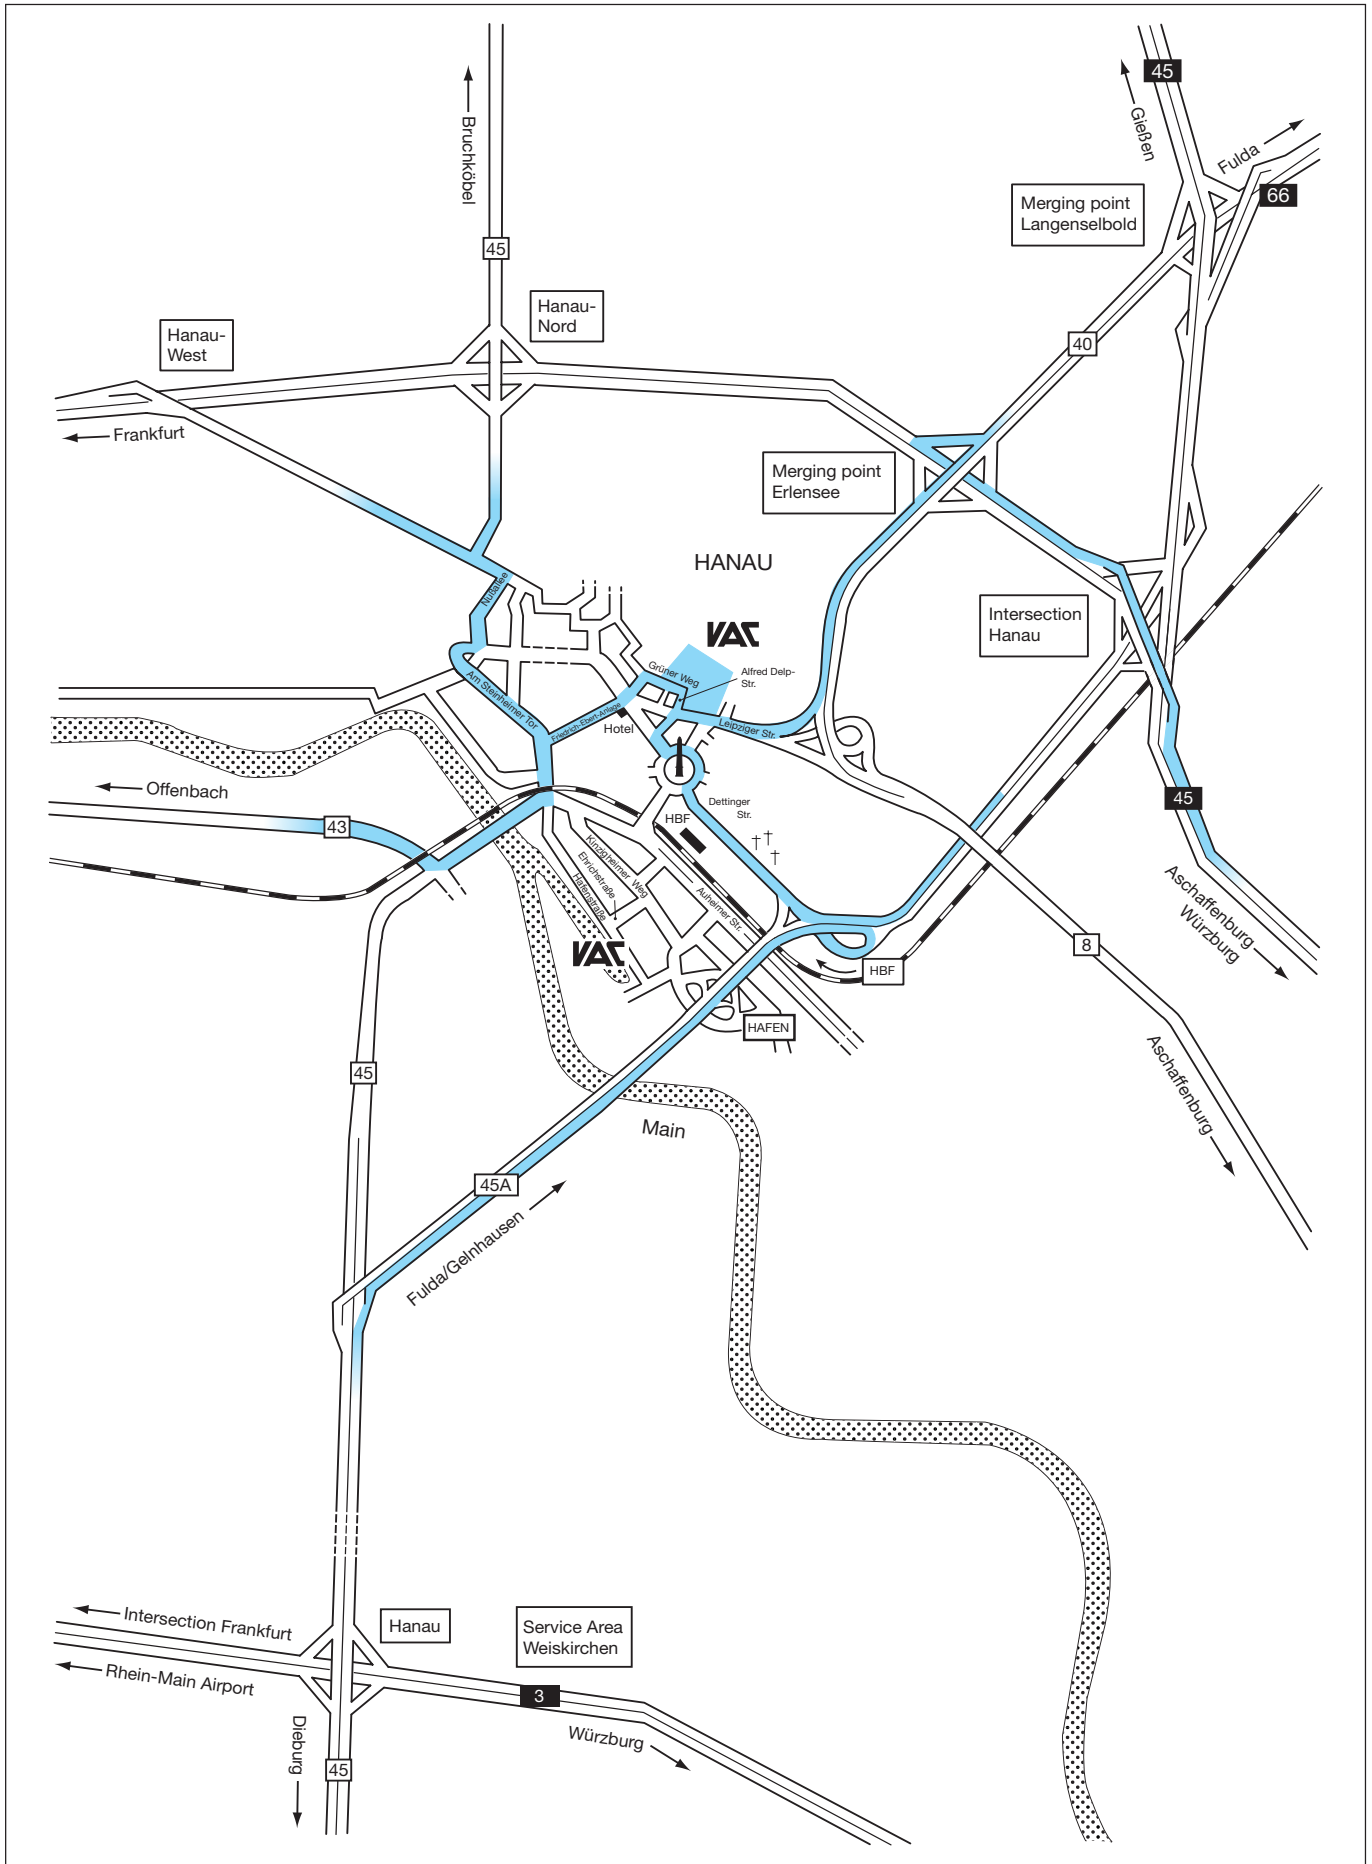

# Product Survey

---

## Semi-Finished Products and Parts

### Metallic Semi-Finished Products

Soft magnetic alloys  
Magnetically semi-hard alloys  
Ductile permanent magnets  
Thermobimetals  
Spring alloys  
Glass/ceramic-to-metal sealing alloys

### Parts

Stamped/bent parts  
Laminations  
Magnetic shielding

### Superconductors

## Cores and Components

### Magnetic Cores

Tape-wound cores made of crystalline, amorphous and nano-crystalline alloys

### Inductive Components

for xDSL, ISDN and switched-mode power supplies,  
for current detection and  
for driving power semiconductors

## Rare-Earth Permanent Magnets

### Magnets on Sm-Co and Nd-Fe-B Base

### Polymer Bonded Magnets

### Magnet Assemblies

---

**VACUUMSCHMELZE GMBH & CO. KG**



Advanced Materials – The Key to Progress

P.O.B. 22 53  
D-63412 Hanau, Germany  
☎ (\*\*49) 61 81/38-0  
☎ (\*\*49) 61 81/38-20 65  
Internet: <http://www.vacuumschmelze.com>  
E-Mail: [info@vacuumschmelze.com](mailto:info@vacuumschmelze.com)

082001

Published by VACUUMSCHMELZE GMBH & CO. KG, Hanau  
© VACUUMSCHMELZE GMBH & CO. KG 2001. All rights reserved.

As far as patents or other rights of third parties are concerned, liability is only assumed for products per se, not for applications, processes and circuits implemented within these products. The information describes the type of product and shall not be considered as assured characteristics. Terms of delivery and rights to change design reserved. This brochure replaces the previous editions.

Printed on chlorine free manufactured paper.